

September 24, 2008Rev.
Epoxy Resin Department

Durability data of ADEKA ULTRASEAL MC-series

1. Purpose,

There is a difficulty to predict durability of materials. Because, it need to consider many condition to estimate its durability. But we have to know materials durability to use it. Degradation of materials is one of chemical reaction, so we can know its durability from heat degradation. Generally, Arrhenius's method is used to estimate durability of materials.

Relationship between speed of chemical reaction and temperature is shown as follows by S. A. Arrhenius in 1889.

$$K = A \exp (-Ea/RT) \text{ -----(1)}$$

K : velocity constant

R : gas constant

T : absolute temperature

A : frequency factor

Ea : activation energy

To estimate materials durability, expression (1) leads expression (2).

$$\ln (t) = Ea/(RT) + \text{const.} \text{ -----(2)}$$

t : hours

Expression (2) means, logarithm of time "t" proportional to (1/T).

So, promoted test results at high temperature can estimate life of materials at normal condition. We choose half-life of material's elongation data to estimate durability of ADEKA ULTRASEAL MC-series.

2. Promoted degradation test

Testing condition is shown at table-1.

Table-1) Testing condition

Test item	Elongation
Temperature	50,70 and 90 degrees C
Predict method	Half-life of elongation
Testing method	JIS K 6251

Result

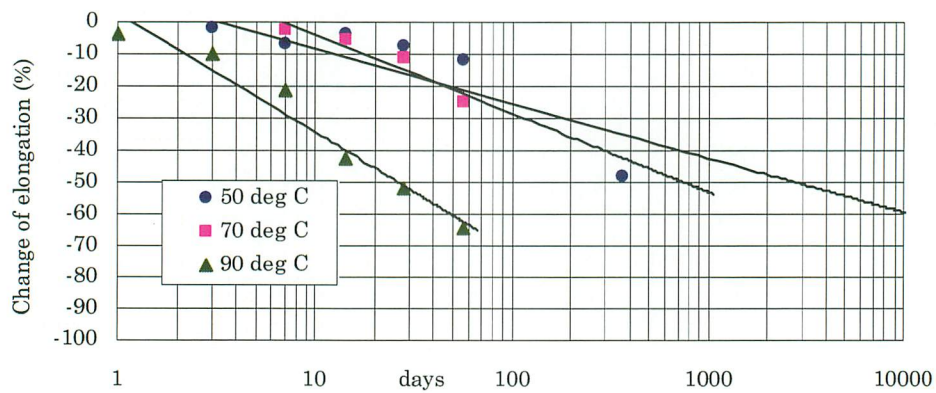


Fig.1) Relationship between change of elongation and days

We can read half-life of elongation from Fig.1) as follows, Expression (3) - (5) show approximate expression of change of elongation and days data.

$$y = -7.3658 \ln(x) + 8.4807 \text{ -----(3)}$$

$$y = -10.674 \ln(x) + 20.74 \text{ -----(4)}$$

$$y = -16.119 \ln(x) + 2.7283 \text{ -----(5)}$$

y : change of elongation

x : days

Temperature (Deg C)/(Deg F)/(K)	Days	t (hrs)
90 / 194 / 363	26	632
70 / 158 / 343	755	18,131
50 / 122 / 323	2,806	67,342

3. Predict of material's life

Expression (2) and Table-1 show relationship of $\ln(t)$ and $1/T$ as follows.

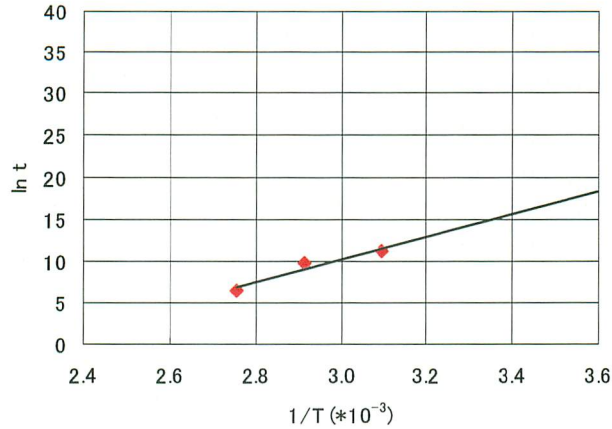


Fig.2) Relationship between $\ln(t)$ and $(1/T)$

$$\ln(t) = 13.552 * (1/T) * 10^3 - 30.476 \text{ -----(6)}$$

Expression (6) leads durability of ADEKA ULTRASEAL MC-series at 20 – 30 degrees C as follows.

Table-2. Durability of ADEKA ULTRASEAL MC-series

Temperature (Deg C)/(Deg F)/(K)	Predicted Durability (years)
20 / 68 / 293	811
25 / 77 / 298	373
30 / 86 / 303	176

This predict method results estimate degradation time at controlled conditions, so these data does not estimate durability at actual condition. Materials are using in many kinds of conditions, so its durability are different in many cases. But this durability data is useful to know ADEKA ULTRASEAL MC-series has good degradation resist ability.

(End)